



ISTITUTO NAZIONALE DI RICERCA METROLOGICA Repository Istituzionale

High concentration Yb-Er co-doped multi-component phosphate glasses for compact eye-safe optical amplifiers

This is the author's accepted version of the contribution published as:

Original

High concentration Yb-Er co-doped multi-component phosphate glasses for compact eye-safe optical amplifiers / Pugliese, Diego; Boetti, Nadia G.; Milanese, Daniel; Janner, Davide. - (2020), pp. 1-4. (Intervento presentato al convegno 22nd International Conference on Transparent Optical Networks (ICTON) tenutosi a Bari nel 19-23 Luglio 2020) [10.1109/ICTON51198.2020.9203163].

Availability:

This version is available at: 11696/77407 since:

Publisher:

IEEE

Published

DOI:10.1109/ICTON51198.2020.9203163

Terms of use:

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

IEEE

© 20XX IEEE. Personal use of this material is permitted. Permission from IEEE must be obtained for all other uses, in any current or future media, including reprinting/republishing this material for advertising or promotional purposes, creating new collective works, for resale or redistribution to servers or lists, or reuse of any copyrighted component of this work in other works

(Article begins on next page)

High concentration Yb-Er co-doped multi-component phosphate glasses for compact eye-safe optical amplifiers

Diego Pugliese^{1*}, Nadia G. Boetti², Daniel Milanese³, Davide Janner¹

¹*Dipartimento di Scienza Applicata e Tecnologia, Politecnico di Torino and RU INSTM, C.so Duca degli Abruzzi 24, 10129 Torino, Italy*

**Tel: +39 011 0904668, Fax: +39 011 0904624, e-mail: diego.pugliese@polito.it*

²*Fondazione LINKS – Leading Innovation & Knowledge for Society, Via P. C. Boggio 61, 10138 Torino, Italy*

³*Dipartimento di Ingegneria e Architettura, Università di Parma and RU INSTM, Parco Area delle Scienze 181/A, 43124 Parma, Italy*

ABSTRACT

In recent years, the increasing need of airborne Light Detection And Ranging (LIDAR) systems for environmental monitoring and surveillance has noticeably boosted the development of compact eye-safe optical amplifiers. In this scenario, multi-component phosphate glasses can be regarded as ideal candidate materials as they can be doped with a large amount of rare-earth (RE) ions without clustering, thus enabling the realization of few-cm long optical amplifier sections featured by high optical gain per unit length.

In this work we will report the ongoing activities and the recent results obtained by our research group on the design, processing and characterization of a series of Yb-Er co-doped phosphate glasses to be used as active materials for the core of a waveguide amplifier. The physical, thermo-mechanical, optical and spectroscopic properties of the prepared glasses have been thoroughly investigated.

Keywords: phosphate glass, Erbium, Ytterbium, spectroscopic analysis, optical amplifier, LIDAR.

1. INTRODUCTION

The development of compact optical amplifiers operating in the eye-safe wavelength region has been recently triggered by the steadily growing demand for LIDAR systems able to guarantee surveillance of borders and sensitive areas [1]. High-power and eye-safe LIDAR sources that have been used for decades are bulky, heavy, and expensive, thus unable to be installed on small/medium Unmanned Aerial Vehicles (UAVs). This issue has been overcome with the more recent production of 1.5 μm Er-doped glass fiber lasers, which allowed reducing both their size and weight.

A flexible and advantageous approach to realize a high-power LIDAR source is the Master Oscillator Power Amplifier (MOPA) configuration [2]: a seed laser with high spectral quality is followed by a single- or multi-stage power amplifier that boosts the output power to achieve the needed energy.

In this context, multi-component non-silica glasses, such as phosphate ones, have demonstrated to be an ideal candidate material for engineering the amplification stage of a pulsed MOPA as they can be doped with a large amount of RE ions (up to 10^{21} ions/cm³) without clustering [3]. This allows the fabrication of a compact active medium with high optical gain per unit length (> 5 dB/m), thus significantly mitigating nonlinear optical effects.

It is worthwhile highlighting that phosphate glasses are also recognized as an ideal host specifically for an Yb³⁺-Er³⁺ co-doped system because of their high emission cross-section, low back energy transfer and low accumulative energy transfer rates [4]. In addition, the energy transfer efficiency from Yb³⁺ to Er³⁺ in phosphate glasses can be as high as 95% due to the large spectral overlap between the Yb³⁺ emission spectrum ($^2F_{5/2} \rightarrow ^2F_{7/2}$) and the Er³⁺ absorption spectrum ($^4I_{15/2} \rightarrow ^4I_{11/2}$) [5]. Moreover, phosphate glasses exhibit a large glass formation region, good thermo-mechanical and chemical properties, low nonlinear refractive index, and no evidence of photo-darkening even at high population inversion [6,7].

Despite noticeable advances have been made in recent years on the fabrication of RE-doped non-silica glasses for LIDAR sources, significant effort in the research activity of the proper host glass composition and of the optimum ratio of Yb³⁺/Er³⁺ ions doping concentration has still to be accomplished. The present manuscript reports our ongoing activities and recent results regarding the design, synthesis and physical, thermo-mechanical, optical, and spectroscopic characterization of a series of multi-component phosphate glasses co-doped with different Yb³⁺/Er³⁺ ions doping concentration ratios to be used as active materials for the core of a waveguide amplifier.

2. EXPERIMENTAL DETAILS

2.1 Glass synthesis

A novel phosphate glass host (P₂O₅ - K₂O - Al₂O₃ - B₂O₃ - BaO - PbO - La₂O₃ - Gd₂O₃), able to incorporate a high amount of RE ions and suitable for fiber drawing, was *ad hoc* designed and developed for this research.

Three different glasses, named for short YE2/1, YE4/1 and YE6/1, were obtained by doping the host material with a fixed level of Er_2O_3 (0.75 mol%) and an increasing level of Yb_2O_3 (ranging from 1.50 to 4.50 mol%). The glass samples were synthesized by conventional melt-quenching technique using high purity (99+%) chemicals.

The chemicals were weighed and mixed within a dry box to minimize the hydroxyl ions (OH^-) content in the glasses. The batched chemicals were melted in an alumina crucible at a temperature of 1400 °C for 1 h inside a chamber furnace under a controlled atmosphere (dry air, water content < 3 ppm) and subsequently cast into a preheated brass cylindrical mold 12 mm in diameter to obtain 10 cm-long rod preforms. The cast glasses were annealed at a temperature around the transition temperature (T_g) for 5 h to relieve internal stresses and finally cooled down slowly to room temperature.

Flat specimens were cut from the three preforms and optically polished to 1 mm-thick samples to be used for optical and spectroscopic characterization. Samples with thicknesses of 12 and 5 mm were used for density and coefficient of thermal expansion (CTE) measurements, respectively, and about 30 mg of fine grain sample were prepared and used for the evaluation of the glass characteristic temperatures.

2.2 Glass characterization

The density (ρ) of the glasses was measured at room temperature with an accuracy of 0.05 g/cm³ by the Archimedes' method using distilled water as the immersion fluid. The concentration of the Yb^{3+} and Er^{3+} ions was calculated through density data in relation to the nominal composition of the glasses.

The characteristic temperatures of the glasses (glass transition temperature T_g and onset crystallization temperature T_x) were measured using a Netzsch DSC 404 F3 Pegasus® differential scanning calorimeter with a heating rate of 5 °C/min in sealed Pt/Rh pans featuring an error of ± 3 °C. The glass stability parameter $\Delta T = T_x - T_g$ was calculated with an error of ± 6 °C.

The CTE was measured by a Netzsch DIL 402 PC horizontal alumina dilatometer operating at 5 °C/min. The measure was automatically interrupted when a shrinkage higher than 0.13% was achieved (softening point T_s). The CTE value was calculated in the 200 - 400 °C temperature range, featuring an error of ± 0.1 °C⁻¹.

The refractive index (n) of the glasses was measured at 5 different wavelengths (632.8, 825, 1061, 1312 and 1533 nm) by prism-coupling technique using a Metricon 2010 Prism Coupler. Ten scans were performed for each wavelength and the estimated error of the measurement was ± 0.001 .

The Fourier transform infrared (FTIR) spectra were taken between 2000 and 7000 cm⁻¹, with a resolution of 4 cm⁻¹ and acquiring an average of 16 scans, using the spectrometer Alpha, Bruker Optics, working in transmission mode and equipped with a deuterated-triglycine sulphate (DTGS) detector. The content of OH^- groups was evaluated through the application of the formula proposed by Ehrmann *et al.* [8], while the typical transmittance FTIR spectrum of the synthesized glasses is reported in terms of optical loss.

The continuous-wave (CW) photoluminescence spectra of the glasses were acquired in the near-infrared (NIR) region by a Jobin Yvon iHR320 spectrometer equipped with a Hamamatsu P4631-02 detector, using standard lock-in technique. The emission spectra were obtained by exciting the samples with a monochromatic light at the wavelength of 976 nm emitted by the fiber pigtailed laser diode Oclaro CM962UF76P-10R.

The fluorescence lifetimes (τ) of $\text{Er}^{3+}{}^4\text{I}_{13/2}$ level were obtained by exciting the samples with light pulses of the 976 nm laser diode. The signal was recorded by a digital oscilloscope (Tektronix TDS350) and the decay traces were fitted by single exponential. Estimated error of the measurement was ± 0.20 ms. The detector used for this measurement was a Thorlabs PDA10CS.

3. RESULTS AND DISCUSSION

Table 1 reports the physical, optical and spectroscopic properties of the synthesized phosphate glass samples.

Table 1. Density (ρ), Yb^{3+} and Er^{3+} ions concentration, refractive index (n) at 1533 nm, OH^- content and excited state ${}^4\text{I}_{13/2}$ lifetime (τ) of the fabricated Yb-Er co-doped multi-component phosphate glasses.

Glass label	ρ [g/cm ³]	Yb^{3+} [$\times 10^{20}$ ions/cm ³]	Er^{3+} [$\times 10^{20}$ ions/cm ³]	n	OH^- content [ppm]	τ [ms]
YE2/1	3.43	3.86	1.93	1.569	435	4.60
YE4/1	3.43	7.69	1.92	1.566	279	5.50
YE6/1	3.43	11.50	1.92	1.564	295	5.50

It is worthwhile noting that the density of the glasses did not change by varying the Yb^{3+} ions doping level, due to the fact that the doping oxide Yb_2O_3 was added in substitution of Gd_2O_3 in the host matrix, both quite close in terms of molecular weight.

The glasses showed typical T_g , T_s , T_x , and CTE values equal to 502 °C, 533 °C, 762 °C, and 11.87×10^{-6} °C⁻¹, respectively. The higher T_g and lower CTE than those reported in literature for other phosphate glass compositions [9] prove that they are markedly robust and resistant to the thermal stress induced by their processing. Moreover, a typical glass stability parameter ΔT of 260 °C was assessed, thus indicating that the synthesized glasses are stable against devitrification and suitable for crystal-free fiber drawing.

Fig. 1 reports a typical IR spectrum of the manufactured glass samples in the region between 2500 and 4000 cm⁻¹. The broad and intense OH⁻ vibration band centered at around 3000 cm⁻¹ provides useful information on the concentration of OH⁻ groups inside the glasses [10]. Free OH⁻ groups are regarded as effective quenchers of the IR radiation in Yb-Er co-doped phosphate glasses, resulting in a noticeable decrease of the Er^{3+:}⁴I_{13/2} lifetime.

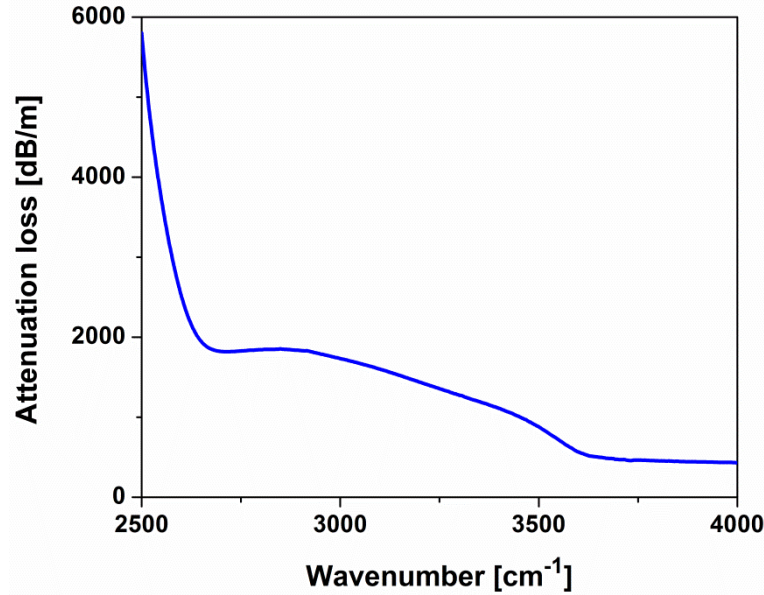


Figure 1. IR spectrum of the YE4/1 glass showing the broad OH⁻ vibration band at 3000 cm⁻¹.

The YE2/1 glass exhibited a greater OH⁻ groups content and consistently a shorter excited state Er^{3+:}⁴I_{13/2} lifetime compared to the YE4/1 and YE6/1 glasses, as evident from the data reported in the last two columns of Table 1. This experimental evidence can possibly be ascribed to a higher absorption of water molecules readily during its weighing and/or melting processes.

Fig. 2 shows the emission spectra of the Yb-Er co-doped phosphate glasses in the wavelength range between 1470 and 1630 nm recorded upon excitation at 976 nm.

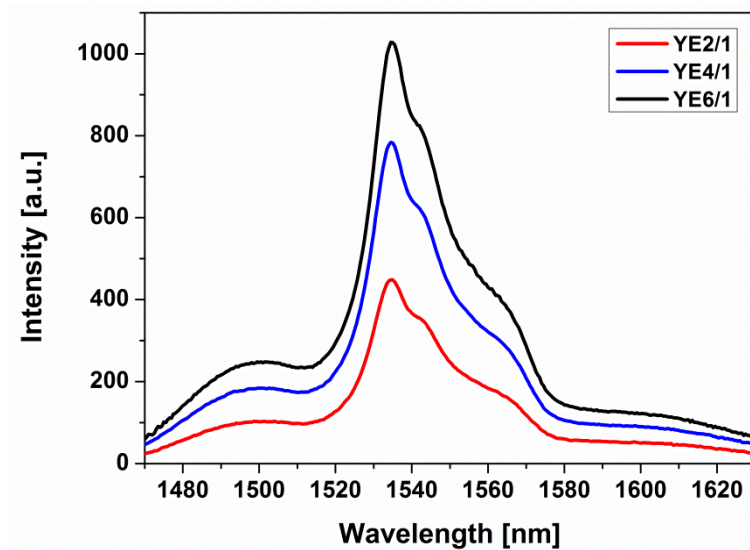


Figure 2. Fluorescence emission spectra of the synthesized glass samples under excitation at 976 nm.

The broad and intense emission peak at around 1535 nm is assigned to the $\text{Er}^{3+}: {}^4\text{I}_{13/2} \rightarrow {}^4\text{I}_{15/2}$ transition and features a full width at half maximum (FWHM) of about 35 nm. It can be observed that the peak height of the emission increases steadily with rising Yb^{3+} ions concentration, due to the increasing absorption of the pump source.

4. CONCLUSIONS

This paper reported on the design, processing and physical, thermo-mechanical, optical, and spectroscopic characterization of novel Yb-Er co-doped phosphate glasses. The glass host developed for this research was able to incorporate up to 10^{21} Er^{3+} and Yb^{3+} ions/ cm^3 without clustering, while the RE-doped glasses resulted to be stable against crystallization and therefore suitable for fiber drawing, resistant to thermal shock and they also showed promising optical and fluorescent properties. In light of all these features, the synthesized phosphate glasses can be profitably employed as active media for the development of compact optical amplifiers for high-power and eye-safe LIDAR sources.

ACKNOWLEDGEMENTS

The reported activity was carried out in the framework of the NATO Science for Peace and Security project “Caliber” (grant no. SPS G5248). The authors wish to acknowledge Politecnico di Torino through the Interdepartmental Center PhotoNext and the COST action MP1401 for the partial support of this research effort.

REFERENCES

- [1] J.R. Kellner, J. Armston, M. Birrer, K.C. Cushman, L. Duncanson, C. Eck, C. Falleger, B. Imbach, K. Král, M. Krůček, J. Trochta, T. Vrška, C. Zraggen: New opportunities for forest remote sensing through ultra-high-density drone lidar, *Surv. Geophys.*, vol. 40, pp. 959-977, May 2019.
- [2] W. Shi, E.B. Petersen, Z. Yao, D.T. Nguyen, J. Zong, M.A. Stephen, A. Chavez-Pirson, N. Peyghambarian: Kilowatt-level stimulated-Brillouin-scattering-threshold monolithic transform-limited 100 ns pulsed fiber laser at 1530 nm, *Opt. Lett.*, vol. 35, pp. 2418-2420, Jul. 2010.
- [3] N.G. Boetti, D. Pugliese, E. Ceci-Ginistrelli, J. Lousteau, D. Janner, D. Milanese: Highly doped phosphate glass fibers for compact lasers and amplifiers: a review, *Appl. Sci.*, vol. 7, art. id. 1295, Dec. 2017.
- [4] V.P. Gapontsev, S.M. Matitsin, A.A. Isineev, V.B. Kravchenko: Erbium glass lasers and their applications, *Opt. Laser Technol.*, vol. 14, pp. 189-196, Aug. 1982.
- [5] B.-C. Hwang, S. Jiang, T. Luo, J. Watson, G. Sorbello, N. Peyghambarian: Cooperative upconversion and energy transfer of new high Er^{3+} - and Yb^{3+} - Er^{3+} -doped phosphate glasses, *J. Opt. Soc. Am. B*, vol. 17, pp. 833-839, May 2000.
- [6] S. Jiang, S.B. Mendes, Y. Hu, G. Nunzi Conti, A. Chavez-Pirson, Y. Kaneda, T. Luo, Q. Chen, S. Hocde, D.T. Nguyen, E.M. Wright, J. Wang, W. Tian, T. Nikolajsen, N. Peyghambarian: Compact multimode pumped erbium-doped phosphate fiber amplifiers, *Opt. Eng.*, vol. 42, pp. 2817-2820, Oct. 2003.
- [7] N.G. Boetti, G.C. Scarpignato, J. Lousteau, D. Pugliese, L. Bastard, J.-E. Broquin, D. Milanese: High concentration Yb-Er co-doped phosphate glass for optical fiber amplification, *J. Opt.*, vol. 17, art. id. 065705, May 2015.
- [8] P.R. Ehrmann, K. Carlson, J.H. Campbell, C.A. Click, R.K. Brow: Neodymium fluorescence quenching by hydroxyl groups in phosphate laser glasses, *J. Non-Cryst. Solids*, vol. 349, pp. 105-114, Dec. 2004.
- [9] Q. Yin, S. Kang, X. Wang, S. Li, D. He, L. Hu: Effect of PbO on the spectral and thermo-optical properties of Nd^{3+} -doped phosphate laser glass, *Opt. Mater.*, vol. 66, pp. 23-28, Apr. 2017.
- [10] D. Pugliese, N.G. Boetti, J. Lousteau, E. Ceci-Ginistrelli, E. Bertone, F. Geobaldo, D. Milanese: Concentration quenching in an Er-doped phosphate glass for compact optical lasers and amplifiers, *J. Alloys Compd.*, vol. 657, pp. 678-683, Feb. 2016.